

Test Report No.: 48.400.23.1087.01-00/17

Rev.: 00

Dated: 2023-11-08



Applicant: Jiangsu Acrel Electrical Manufacturing. Co., Ltd.  
Address: No. 5, Dongmeng Road, Nanzha Street, Jiangyin, Jiangsu, P. R. China  
Attn: Han Zhonghua  
Sample Description: Current transformer  
Model No.: AKH-0.66K-TD  
Sample Received Date: 2023-10-12  
Test Period: 2023-10-12~2023-10-27  
Test Location: TÜV SÜD Certification and Testing (China) Co., Ltd.  
Shanghai Branch, SHA Chemical Lab.  
Purpose of examination: Verification of RoHS (Restriction of Hazardous Substances) directive 2011/65/EU and its amendment (EU) 2015/863 on submitted samples  
Test Results: Refer to following page(s)  
Remark:  
- The result relates only to the items tested.  
- The reference model(s) was declared by client.  
- The test sample(s) and item(s) was specified by client.

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24

TÜV SÜD Certification and Testing (China) Co., Ltd.  
TÜV SÜD Group  
Prepared by:



Mr. Yiwei CHEN

Reviewed by:



Mr. Feng ZHANG

Disclaimer Measurement Uncertainty: Unless otherwise agreed upon, Pass or Fail verdicts are given base on the measured values without any considerations of measurement uncertainties. Please note, every test method has a measurement uncertainty which has been evaluated by the laboratory according to ISO/IEC 17025 requirements. By taking measurement uncertainties into account it might happen that measured values can neither be assessed as Pass nor as Fail. Any use for advertising purposes must be granted in writing. This test report may only be quoted in full. This report is the result of a single examination of the object in question and is not generally applicable evaluation of the quality of other products in regular production. For further details, please see testing and certification regulation, chapter A-3.4.

TÜV SÜD Certification and Testing (China) Co., Ltd.  
Floor 1-4, Building B, No.37, Tuanjie Road(Middle), Xishan  
Economic and Technological Development Zone, Wuxi  
Jiangsu. China

Tel.: +86-510-88203737 Fax: +86-510-88203636

www.tuv-sud.cn info@tuv-sud.cn

Shanghai Chemical Lab No. 1999 Du Hui Road  
Tel.: +86-21-6037-6501

Test Report No.: 48.400.23.1087.01-00/17

Rev.: 00

Dated: 2023-11-08



### SUMMARY OF TEST RESULTS

No.	Test Requested	Conclusion	Remarks
1.	Heavy Metal (Pb, Cd, Hg and Cr VI) Content	<b>PASS</b>	
2.	Polybrominated Biphenyls (PBBs) and Polybrominated Diphenyl Ethers (PBDEs) Content	<b>PASS</b>	
3.	Phthalates (DEHP, BBP, DBP and DIBP) Content	<b>PASS</b>	

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24








1. TESTED SUBJECT DESCRIPTION

Sample No.	Description (Material, colour)	Photograph/Location
01	White soft plastic tie band	
02	Black hard plastic shell	
03	Green paper cushion	
04	Red sponge cushion	
05	Silvery metal spring	

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24

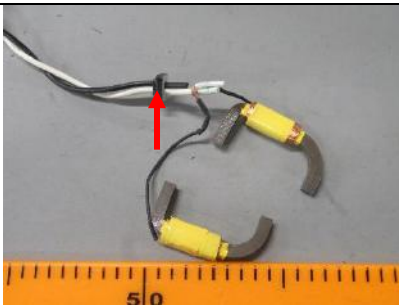


TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24

Sample No.	Description (Material, colour)	Photograph/Location
06	black hard plastic component	
07	Black soft plastic heat shrinkable tube	
08	Yellow soft plastic adhesive tape	
09	Golden metal wire	
10	Silvery metal magnet	



Sample No.	Description (Material, colour)	Photograph/Location
11	Black soft plastic wire jacket	
12	White soft plastic wire jacket	
13	Silvery metal wire	

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24

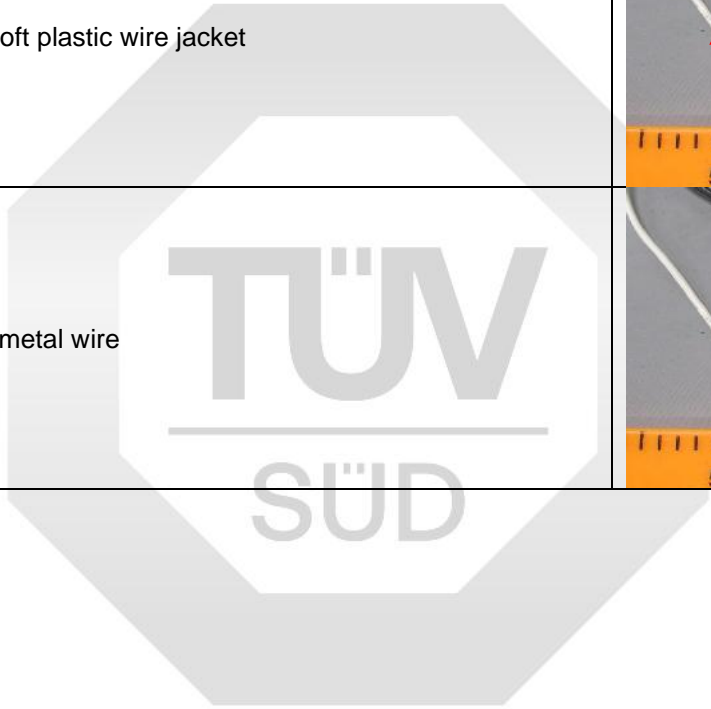



2. TEST RESULT(S)

2.1 SCREENING TEST

Test method: With reference to EN 62321-1:2013, EN IEC 62321-2:2021, EN 62321-3-1:2014 and EN 62321-8:2017.

For Heavy Metals and Flame Retardants, analyzed by Energy Dispersive X-ray Fluorescence Spectrometer (XRF); for phthalates, analyzed by Gas Chromatography and Mass Spectrometer (GC-MS).

Sample No.	Heavy Metals and Flame Retardants					Phthalates			
	Cd	Pb	Hg	Cr	Br	DEHP	BBP	DBP	DIBP
01	BL	BL	BL	BL	BL	BL	BL	BL	BL
02	BL	BL	BL	BL	Inc. <sup>(a)</sup>	BL	BL	BL	BL
03	BL	BL	BL	BL	BL	BL	BL	BL	BL
04	BL	BL	BL	BL	BL	BL	BL	BL	BL
05	BL	BL	BL	Inc. <sup>(a)</sup>	NA	NA	NA	NA	NA
06	BL	BL	BL	BL	BL	BL	BL	BL	BL
07	BL	BL	BL	BL	BL	BL	BL	BL	BL
08	BL	BL	BL	BL	BL	BL	BL	BL	BL
09	BL	BL	BL	BL	NA	NA	NA	NA	NA
10	BL	BL	BL	Inc. <sup>(a)</sup>	NA	NA	NA	NA	NA
11	BL	BL	BL	BL	BL	BL	BL	BL	BL
12	BL	BL	BL	BL	BL	BL	BL	BL	BL
13	BL	BL	BL	BL	NA	NA	NA	NA	NA

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24



Remark:

- "BL" denotes below limit
- "OL" denotes over limit
- "Inc." denotes inconclusive
- "NA" denotes not applicable
- "(a)" denotes further confirmation test was conducted, results are listed in 2.2 and 2.3.
- XRF screening limits in mg/kg for regulated elements in various matrices

ELEMENT	POLYMER		
	BL	INCONCLUSIVE	OL
Cd	$X \leq (70-3\sigma)$	$(70-3\sigma) < X < (130+3\sigma)$	$X \geq (130+3\sigma)$
Pb	$X \leq (700-3\sigma)$	$(700-3\sigma) < X < (1300+3\sigma)$	$X \geq (1300+3\sigma)$
Hg	$X \leq (700-3\sigma)$	$(700-3\sigma) < X < (1300+3\sigma)$	$X \geq (1300+3\sigma)$
Br	$X \leq (300-3\sigma)$	$X > (300-3\sigma)$	NA
Cr	$X \leq (700-3\sigma)$	$X > (700-3\sigma)$	NA

ELEMENT	METAL		
	BL	INCONCLUSIVE	OL
Cd	$X \leq (70-3\sigma)$	$(70-3\sigma) < X < (130+3\sigma)$	$X \geq (130+3\sigma)$
Pb	$X \leq (700-3\sigma)$	$(700-3\sigma) < X < (1300+3\sigma)$	$X \geq (1300+3\sigma)$
Hg	$X \leq (700-3\sigma)$	$(700-3\sigma) < X < (1300+3\sigma)$	$X \geq (1300+3\sigma)$
Cr	$X \leq (700-3\sigma)$	$X > (700-3\sigma)$	NA

ELEMENT	COMPLEX MATERIAL		
	BL	INCONCLUSIVE	OL
Cd	$X \leq (50-3\sigma)$	$(50-3\sigma) < X < (150+3\sigma)$	$X \geq (150+3\sigma)$
Pb	$X \leq (500-3\sigma)$	$(500-3\sigma) < X < (1500+3\sigma)$	$X \geq (1500+3\sigma)$
Hg	$X \leq (500-3\sigma)$	$(500-3\sigma) < X < (1500+3\sigma)$	$X \geq (1500+3\sigma)$
Br	$X \leq (250-3\sigma)$	$X > (250-3\sigma)$	NA
Cr	$X \leq (500-3\sigma)$	$X > (500-3\sigma)$	NA

- Screening limits in mg/kg for regulated phthalates in various matrices

PHTHALATES	BL	INCONCLUSIVE
DEHP	$X < 600$	$X \geq 600$
BBP	$X < 600$	$X \geq 600$
DBP	$X < 600$	$X \geq 600$
DIBP	$X < 600$	$X \geq 600$

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24



## 2.2 HEAVY METAL CONTENT

Test method: With reference to EN 62321-4:2014 /A1:2017, EN 62321-5:2014, EN 62321-7-1:2015 and EN 62321-7-2:2017, analyzed by Inductively Coupled Plasma Optical Emission Spectrometer (ICP-OES) and Ultraviolet-visible spectrophotometer (UV-Vis).

[Reporting Limit: 2.0 mg/kg for Cadmium; 5.0 mg/kg or 0.10 µg/cm<sup>2</sup> for Hexavalent Chromium, 10.0 mg/kg for Lead and Mercury.]

Sample No.	Result(s)				
	Total Cadmium	Hexavalent Chromium	Hexavalent Chromium	Total Mercury	Total Lead
05	--	/	Negative	--	--
10	--	/	Negative	--	--
Unit	mg/kg	mg/kg	µg/cm <sup>2</sup>	mg/kg	mg/kg
RoHS Requirement	100	1000	Negative <sup>#</sup>	1000	1000

Remark:

- "mg/kg" denotes milligram per kilogram
- "µg/cm<sup>2</sup>" denotes micrograms per square centimeter
- "<" denotes less than
- "Positive" denotes the absorbance value of sample is > 0.13 µg/cm<sup>2</sup>, the sample is considered to be positive for Hexavalent Chromium.
- "Inconclusive" denotes the absorbance value of sample is ≥ 0.10 µg/cm<sup>2</sup> and ≤ 0.13 µg/cm<sup>2</sup>, the sample is considered to be Inconclusive for Hexavalent Chromium.
- "Negative" denotes the absorbance value of sample is < 0.10 µg/cm<sup>2</sup>, the sample is considered to be negative for Hexavalent Chromium.
- "<sup>#</sup>" According to DIRECTIVE 2011/65/EU Article 4(1) and Annex II. While, positive means the presence of CrVI on tested areas and the result(s) was (were) regarded as in conflict with European Parliament and Council Directive 2011/65/EU, Article 4(1) and Annex II.
- "--" denotes tested by XRF, result is listed in 2.1

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24





**2.3 POLYBROMINATED BIPHENYLS (PBBs) AND POLYBROMINATED DIPHENYL ETHERS (PBDEs) CONTENT**

Test Method: With reference to EN 62321-6:2015, extracted by toluene and analyzed by Gas Chromatography and Mass Spectrometer (GC-MS). [Reporting Limit : 5 mg/kg]

Test Item		Result(s) [mg/kg]	RoHS Requirement [mg/kg]
		02	
PBBs	Monobromobiphenyl	<5	-
	Dibromobiphenyl	<5	-
	Tribromobiphenyl	<5	-
	Tetrabromobiphenyl	<5	-
	Pentabromobiphenyl	<5	-
	Hexabromobiphenyl	<5	-
	Heptabromobiphenyl	<5	-
	Octabromobiphenyl	<5	-
	Nonabromobiphenyl	<5	-
	Decabromobiphenyl	<5	-
	<b>Sum of detected PBBs</b>	<50	1000
PBDEs	Monobromodiphenyl ether	<5	-
	Dibromodiphenyl ether	<5	-
	Tribromodiphenyl ether	<5	-
	Tetrabromodiphenyl ether	<5	-
	Pentabromodiphenyl ether	<5	-
	Hexabromodiphenyl ether	<5	-
	Heptabromodiphenyl ether	<5	-
	Octabromodiphenyl ether	<5	-
	Nonabromodiphenyl ether	<5	-
	Decabromodiphenyl ether	<5	-
	<b>Sum of detected PBDEs</b>	<50	1000

Remark:

- "mg/kg" denotes milligram per kilogram
- "<" denotes less than

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24

Test Report No.: 48.400.23.1087.01-00/17

Rev.: 00

Dated: 2023-11-08



## 2.4 PHTHALATES (DEHP, BBP, DBP and DIBP) CONTENT TEST

Test method: With reference to EN 62321-8:2017, extracted by organic solvent and analyzed by Gas Chromatography and Mass Spectrometer (GC-MS). [Reporting Limit : 50 mg/kg]

Test Item	Result(s) [mg/kg]	RoHS Requirement [mg/kg]
	07	
Di-iso-butyl Phthalate (DIBP)	<50	<1000
Di-butyl Phthalate (DBP)	<50	<1000
Butyl-benzyl Phthalate (BBP)	<50	<1000
Di-(2-ethyl-hexyl) Phthalate (DEHP)	76	<1000

Remark:

- "mg/kg" denotes milligram per kilogram
- "<" denotes less than



TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24


Test Report No.: 48.400.23.1087.01-00/17

Rev.: 00

Dated: 2023-11-08




**APPENDIX I: Product Model**

Product: Current transformer	Test model: AKH-0.66K-TD
	

**Remark:**

1. The report covers material testing on specified samples.

**--END OF REPORT--**

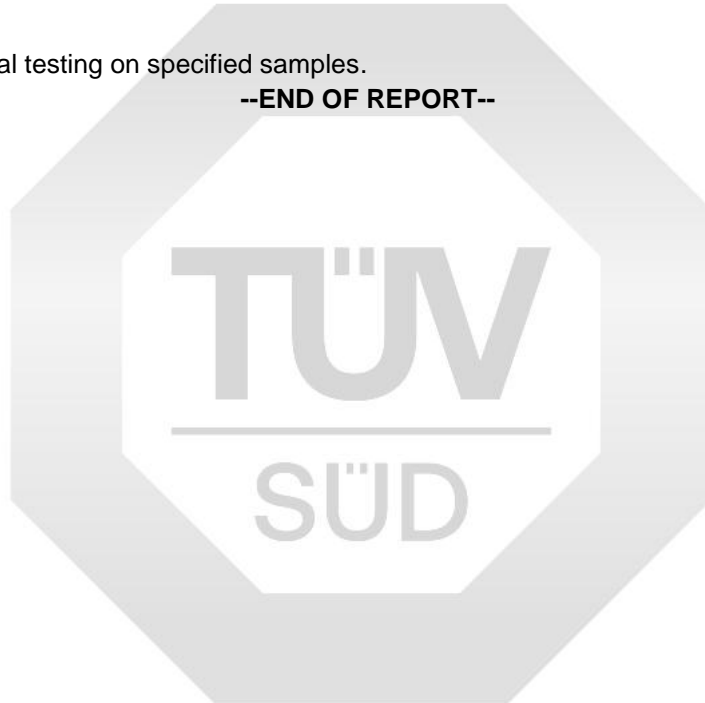

TEC\_WUX\_F\_25.05E - Rev. 00 2021-06-24